

LIDT TEST RESULTS

LIDT VALUE

 10^6-on-1
 $0.187^{+0.016}_{-0.016} \text{ J/cm}^2$

CHARACTERISTIC DAMAGE CURVE

Table 1: Estimated LIDTs from fitting model for sample CAM365_2 HSCH.

Test mode	Threshold (Catastrophic)	Threshold (Color mode)
1-on-1	$1.167^{+0.040}_{-0.039} \text{ J/cm}^2$	-
10-on-1	$1.160^{+0.047}_{-0.046} \text{ J/cm}^2$	-
10^2-on-1	$1.105^{+0.051}_{-0.050} \text{ J/cm}^2$	-
10^3-on-1	$1.067^{+0.051}_{-0.050} \text{ J/cm}^2$	-
10^4-on-1	$1.067^{+0.051}_{-0.050} \text{ J/cm}^2$	$0.577^{+0.042}_{-0.041} \text{ J/cm}^2$
10^5-on-1	$1.012^{+0.034}_{-0.033} \text{ J/cm}^2$	$0.450^{+0.040}_{-0.039} \text{ J/cm}^2$
10^6-on-1	$0.985^{+0.031}_{-0.030} \text{ J/cm}^2$	$0.187^{+0.016}_{-0.016} \text{ J/cm}^2$

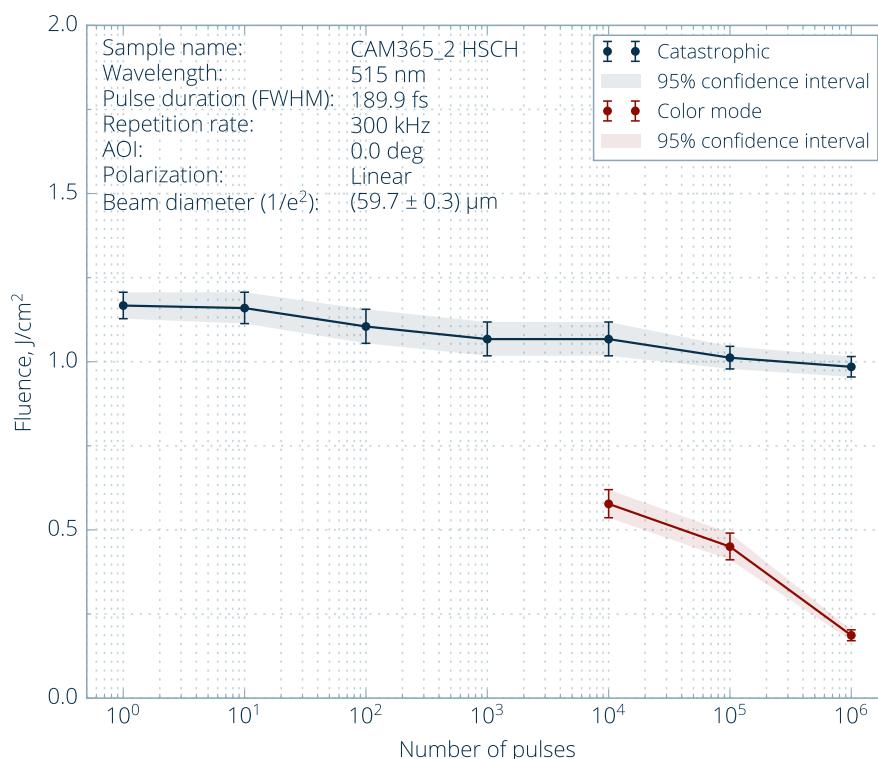


Figure 2. Characteristic damage curve.